

# Chemomagnetism, magnetoconcentration effect and “fishtail” anomaly in chemically-induced granular superconductors

S. A. Sergeenkov

*Unità di Ricerca INFM, Università di L'Aquila, Località Monteluco, 67040 Roio Poggio, Italy*

*Laboratory of Theoretical Physics, Joint Institute for Nuclear Research,  
141980 Dubna, Russia*

Submitted 25 November 2002

Resubmitted 16 December 2002

Within a 2D model of Josephson junction arrays (created by 2D network of twin boundary dislocations with strain fields acting as an insulating barrier between hole-rich domains in underdoped crystals), a few novel effects expected to occur in intrinsically granular material are predicted including: (i) Josephson chemomagnetism (chemically induced magnetic moment in zero applied magnetic field) and its influence on a low-field magnetization (chemically induced paramagnetic Meissner effect), and (ii) magnetoconcentration effect (creation of oxygen vacancies in applied magnetic field) and its influence on a high-field magnetization (chemically induced analog of “fishtail” anomaly). The conditions under which these effects can be experimentally measured in non-stoichiometric high- $T_c$  superconductors are discussed.

PACS: 61.72.-y, 74.25.Ha, 74.50.+r, 74.72.-h

1. Recent STM-based imaging of the granular structure in underdoped  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$  crystals [1], revealed an apparent segregation of its electronic structure into superconducting domains (of the order of a few nanometers) located in an electronically distinct background. In particular, it was found that at low levels of hole doping ( $\delta < 0.2$ ), the holes become concentrated at certain hole-rich domains. (In this regard, it is interesting to mention a somewhat similar phenomenon of “chemical localization” that takes place in materials, composed of atoms of only metallic elements, exhibiting metal-insulator transitions [2].) Tunneling between such domains leads to intrinsic granular superconductivity (GS) in high- $T_c$  superconductors (HTS). Probably one of the first examples of GS was observed in  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  single crystals in the form of the so-called “fishtail” anomaly of magnetization [3]. The granular behavior has been related to the 2D clusters of oxygen defects forming twin boundaries (TBs) or dislocation walls within CuO plane that restrict supercurrent flow and allow excess flux to enter the crystal. Indeed, there are serious arguments to consider the TB in HTS as insulating regions of the Josephson SIS-type structure. An average distance between boundaries is essentially less than the grain size. In particular, the networks of localized grain boundary dislocations with the spacing ranged from 10 nm to 100 nm have been observed [3] which produce effectively continuous normal or insulating barriers at the grain boundaries. It was also verified that the processes of the oxygen ordering in HTS leads to the

continuous change of the lattice period along TB with the change of the oxygen content. Besides, a destruction of bulk superconductivity in these non-stoichiometric materials with increasing the oxygen deficiency parameter  $\delta$  was found to follow a classical percolation theory [4].

In addition to their importance for understanding the underlying microscopic mechanisms governing HTS materials, the above experiments can provide rather versatile tools for designing chemically-controlled atomic scale Josephson junctions (JJs) and their arrays (JJAs) with pre-selected properties needed for manufacturing the modern quantum devices [5, 6]. Moreover, as we shall see below, GS based phenomena can shed some light on the origin and evolution of the so-called paramagnetic Meissner effect (PME) which manifests itself both in high- $T_c$  and conventional superconductors [7, 8] and is usually associated with the presence of  $\pi$ -junctions and/or unconventional ( $d$ -wave) pairing symmetry. Since recently, much attention has been paid to both experimental and theoretical study of PME related effects using specially designed SFS-type junctions [9, 10].

In this Letter, within a 2D model of JJAs (created by a regular 2D network of TB dislocations), we discuss a possibility of a few novel interesting effects which are expected to occur in intrinsically granular non-stoichiometric material. In particular, we shall consider (i) Josephson chemomagnetism (chemically induced magnetic moment in zero applied magnetic field) and its influence on a low-field magnetization (chemi-

cally induced PME), and (ii) magnetoconcentration effect (creation of extra oxygen vacancies in applied magnetic field) and its influence on a high-field magnetization (chemically induced analog of "fishtail" anomaly).

**2. The scenario.** As is well-known, the presence of a homogeneous chemical potential  $\mu$  through a single JJ leads to the AC Josephson effect with time dependent phase difference  $\partial\phi/\partial t = \mu/\hbar$ . In this paper, we will consider some effects in dislocation induced JJ caused by a local variation of excess hole concentration  $c(\mathbf{x})$  under the chemical pressure (described by inhomogeneous chemical potential  $\mu(\mathbf{x})$ ) equivalent to presence of the strain field of 2D dislocation array  $\epsilon(\mathbf{x})$  forming this Josephson contact.

To understand how GS manifests itself in non-stoichiometric crystals, let us invoke an analogy with the previously discussed dislocation models of grain-boundary Josephson junctions (GBJJs) (see, e.g., [11, 12] and further references therein). Recall that under plastic deformation, grain boundaries (GBs) (which are the natural sources of weak links in HTS), move rather rapidly via the movement of the grain boundary dislocations (GBDs) comprising these GBs. Using the above evidence, in the previous paper [12] we studied numerous piezomagnetic effects in granular superconductors under mechanical loading. At the same time, observed [1, 3, 13–15] in HTS single crystals regular 2D dislocation networks of oxygen depleted regions (generated by the dissociation of  $\langle 110 \rangle$  twinning dislocations) with the size  $d_0$  of a few Burgers vectors, forming a triangular lattice with a spacing  $d \geq d_0$  ranging from 10 nm to 100 nm, can provide quite a realistic possibility for existence of 2D Josephson network within CuO plane. Recall furthermore that in a  $d$ -wave orthorhombic YBCO crystal TBs are represented by tetragonal regions (in which all dislocations are equally spaced by  $d_0$  and have the same Burgers vector  $\mathbf{a}$  parallel to  $y$ -axis within  $CuO$  plane) which produce screened strain fields [14]  $\epsilon(\mathbf{x}) = \epsilon_0 e^{-|\mathbf{x}|/d_0}$  with  $|\mathbf{x}| = \sqrt{x^2 + y^2}$ .

Though in  $YBa_2Cu_3O_{7-\delta}$  the ordinary oxygen diffusion  $D = D_0 e^{-U_d/k_B T}$  is extremely slow even near  $T_c$  (due to a rather high value of the activation energy  $U_d$  in these materials, typically  $U_d \simeq 1$  eV), in underdoped crystals (with oxygen-induced dislocations) there is a real possibility to facilitate oxygen transport via the so-called osmotic (pumping) mechanism [16, 17] which relates a local value of the chemical potential (chemical pressure)  $\mu(\mathbf{x}) = \mu(0) + \nabla\mu \cdot \mathbf{x}$  with a local concentration of point defects as follows  $c(\mathbf{x}) = e^{-\mu(\mathbf{x})/k_B T}$ . Indeed, when in such a crystal there exists a nonequilibrium concentration of vacancies, dislocation is moved for atomic distance  $a$  by adding excess vacancies to the

extraplane edge. The produced work is simply equal to the chemical potential of added vacancies. What is important, this mechanism allows us to explicitly incorporate the oxygen deficiency parameter  $\delta$  into our model by relating it to the excess oxygen concentration of vacancies  $c_v \equiv c(0)$  as follows  $\delta = 1 - c_v$ . As a result, the chemical potential of the single vacancy reads  $\mu_v \equiv \mu(0) = -k_B T \log(1 - \delta) \simeq k_B T \delta$ . Remarkably, the same osmotic mechanism was used by Gurevich and Pashitskii [14] to discuss the modification of oxygen vacancies concentration in the presence of the TB strain field. In particular, they argue that the change of  $\epsilon(\mathbf{x})$  under an applied or chemically induced pressure results in a significant oxygen redistribution producing a highly inhomogeneous filamentary structure of oxygen-deficient nonsuperconducting regions along GB [15] (for underdoped superconductors, the vacancies tend to concentrate in the regions of compressed material). Hence, assuming the following connection between the variation of mechanical and chemical properties of planar defects, namely  $\mu(\mathbf{x}) = K\Omega_0\epsilon(\mathbf{x})$  (where  $\Omega_0$  is an effective atomic volume of the vacancy and  $K$  is the bulk elastic modulus), we can study the properties of TB induced JJs under intrinsic chemical pressure  $\nabla\mu$  (created by the variation of the oxygen doping parameter  $\delta$ ). More specifically, a single SIS type junction (comprising a Josephson network) is formed around TB due to a local depression of the superconducting order parameter  $\Delta(\mathbf{x}) \propto \epsilon(\mathbf{x})$  over distance  $d_0$  producing thus a weak link with (oxygen deficiency  $\delta$  dependent) Josephson coupling  $J(\delta) = \epsilon(\mathbf{x})J_0 = J_0(\delta)e^{-|\mathbf{x}|/d_0}$  where  $J_0(\delta) = \epsilon_0 J_0 = (\mu_v/K\Omega_0)J_0 \simeq (k_B T J_0/K\Omega_0)\delta$  (here  $J_0 \propto \Delta_0/R_n$  with  $R_n$  being a resistance of the junction). Thus, the considered here model indeed describes chemically induced GS in underdoped systems (with  $\delta \neq 0$ ) because, in accordance with the observations, for stoichiometric situation (when  $\delta \rightarrow 0$ ), the Josephson coupling  $J(\delta) \rightarrow 0$  and the system loses its explicitly granular signature.

**3. The model.** To adequately describe chemomagnetic properties of an intrinsically granular superconductor, we employ a model of 2D overdamped Josephson junction array which is based on the well known tunneling Hamiltonian

$$\mathcal{H}(t) = \sum_{ij}^N J_{ij} [1 - \cos \phi_{ij}(t)] \quad (1)$$

and introduces a short-range (nearest-neighbor) interaction between  $N$  junctions (which are formed around oxygen-rich superconducting areas with phases  $\phi_i(t)$ ), arranged in a two-dimensional (2D) lattice with co-

ordinates  $\mathbf{x}_i = (x_i, y_i)$ . The areas are separated by oxygen-poor insulating boundaries (created by TB strain fields  $\epsilon(\mathbf{x}_{ij})$ ) producing a short-range Josephson coupling  $J_{ij} = J_0(\delta)e^{-|\mathbf{x}_{ij}|/d}$ . Thus, typically for granular superconductors, the Josephson energy of the array varies exponentially with the distance  $\mathbf{x}_{ij} = \mathbf{x}_i - \mathbf{x}_j$  between neighboring junctions (with  $d$  being an average junction size).

If, in addition to chemical pressure  $\nabla\mu(\mathbf{x}) = K\Omega_0\nabla\epsilon(\mathbf{x})$ , the network of superconducting grains is under the influence of an applied frustrating magnetic field  $\mathbf{B}$ , the total phase difference through the contact reads

$$\phi_{ij}(t) = \phi_{ij}^0 + \frac{\pi w}{\Phi_0}(\mathbf{x}_{ij} \wedge \mathbf{n}_{ij}) \cdot \mathbf{B} + \frac{\nabla\mu \cdot \mathbf{x}_{ij}t}{\hbar}, \quad (2)$$

where  $\phi_{ij}^0$  is the initial phase difference (see below),  $\mathbf{n}_{ij} = \mathbf{X}_{ij}/|\mathbf{X}_{ij}|$  with  $\mathbf{X}_{ij} = (\mathbf{x}_i + \mathbf{x}_j)/2$ , and  $w = 2\lambda_L(T) + l$  with  $\lambda_L$  being the London penetration depth of superconducting area and  $l$  an insulator thickness (which, within the discussed here scenario, is simply equal to the TB thickness [17]).

To neglect the influence of the self-field effects in a real material, the corresponding Josephson penetration length  $\lambda_J = \sqrt{\Phi_0/2\pi\mu_0 j_c w}$  must be larger than the junction size  $d$ . Here  $j_c$  is the critical current density of superconducting (hole-rich) area. As we shall see below, this condition is rather well satisfied for HTS single crystals.

**4. Chemomagnetism.** Within our scenario, the sheet magnetization  $\mathbf{M}$  of 2D granular superconductor is defined via the average Josephson energy of the array

$$\langle \mathcal{H} \rangle = \int_0^\tau \frac{dt}{\tau} \int \frac{d^2x}{s} \mathcal{H}(\mathbf{x}, t) \quad (3)$$

as follows

$$\mathbf{M}(\mathbf{B}, \delta) \equiv -\frac{\partial \langle \mathcal{H} \rangle}{\partial \mathbf{B}}, \quad (4)$$

where  $s = 2\pi d^2$  is properly defined normalization area,  $\tau$  is a characteristic Josephson time, and we made a usual substitution

$$\frac{1}{N} \sum_{ij} A_{ij}(t) \rightarrow \frac{1}{s} \int d^2x A(\mathbf{x}, t)$$

valid in the long-wavelength approximation [18].

To capture the very essence of the superconducting analog of the chemomagnetic effect, in what follows we assume for simplicity that a *stoichiometric sample* (with  $\delta = 0$ ) does not possess any spontaneous magnetization at zero magnetic field (that is  $M(0, 0) = 0$ ) and

that its Meissner response to a small applied field  $B$  is purely diamagnetic (that is  $M(B, 0) \simeq -B$ ). According to Eq.(4), this condition implies  $\phi_{ij}^0 = 2\pi m$  for the initial phase difference with  $m = 0, \pm 1, \pm 2, \dots$

Taking the applied magnetic field along the  $c$ -axis (and normal to the CuO plane), that is  $\mathbf{B} = (0, 0, B)$ , we obtain finally

$$M(B, \delta) = -M_0(\delta) \frac{b - b_\mu}{(1 + b^2)(1 + (b - b_\mu)^2)} \quad (5)$$

for the chemically-induced sheet magnetization of the 2D Josephson network.

Here  $M_0(\delta) = J_0(\delta)/B_0$  with  $J_0(\delta)$  defined earlier,  $b = B/B_0$ , and  $b_\mu = B_\mu/B_0 \simeq (k_B T \tau / \hbar) \delta$  where  $B_\mu(\delta) = (\mu_v(\delta) \tau / \hbar) B_0$  is the chemically-induced contribution (which disappears in optimally doped systems with  $\delta = 0$ ), and  $B_0 = \Phi_0 / wd$  is a characteristic Josephson field.

Fig.1 shows changes of the initial (stoichiometric) diamagnetic magnetization  $M/M_0$  (solid line) with oxy-

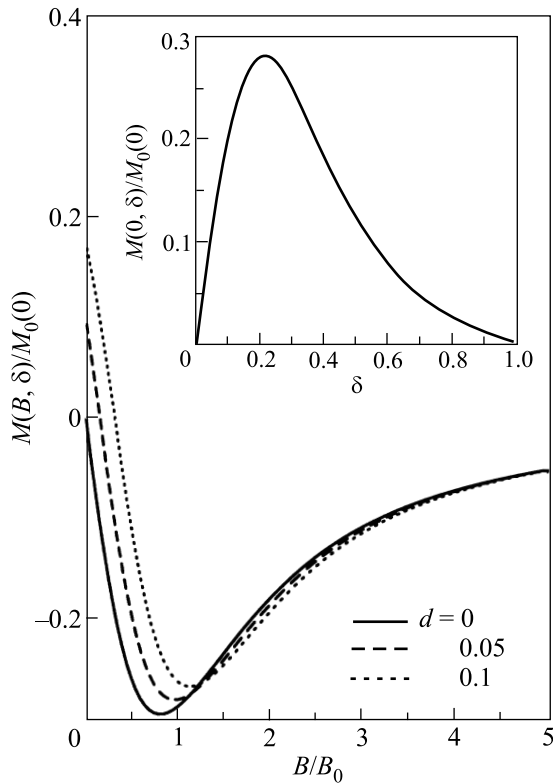


Fig.1. The magnetization  $M(B, \delta)/M_0(0)$  as a function of applied magnetic field  $B/B_0$ , according to Eq.(5), for different values of oxygen deficiency parameter:  $\delta = 0$  (solid line),  $\delta = 0.05$  (dashed line), and  $\delta = 0.1$  (dotted line). Inset:  $\delta$  induced magnetization  $M(0, \delta)/M_0(0)$  in a zero applied magnetic field (chemomagnetism)

gen deficiency  $\delta$ . As is seen, even relatively small values of  $\delta$  parameter render a low field Meissner phase strongly paramagnetic (dotted and dashed lines). The inset of Fig.1 presents a true *chemomagnetic* effect with concentration (deficiency) induced magnetization  $M(0, \delta)$  in zero magnetic field. According to Eq.(5), the initially diamagnetic Meissner effect turns paramagnetic as soon as the chemomagnetic contribution  $B_\mu(\delta)$  exceeds an applied magnetic field  $B$ . To see whether this can actually happen in a real material, let us estimate a magnitude of the chemomagnetic field  $B_\mu$ . Typically [3, 14], for HTS single crystals  $\lambda_L(0) \approx 150$  nm and  $d \approx 10$  nm, leading to  $B_0 \approx 0.5$  T. Using  $\tau \approx \hbar/\mu_v$  and  $j_c = 10^{10}$  A/m<sup>2</sup> as a pertinent characteristic time and the typical value of the critical current density, respectively, we arrive at the following estimate of the chemomagnetic field  $B_\mu(\delta) \approx 0.5B_0$  for  $\delta = 0.05$ . Thus, the predicted chemically induced PME should be observable for applied magnetic fields  $B \approx 0.5B_0 \approx 0.25$  T (which are actually much higher than the fields needed to observe the previously discussed [12] piezomagnetism and stress induced PME in high- $T_c$  ceramics). Notice that for the above set of parameters, the Josephson length  $\lambda_J \approx 1 \mu m$ , which means that the assumed in this paper small-junction approximation (with  $d \ll \lambda_J$ ) is valid and the so-called “self-field” effects can be safely neglected.

**5. Magnetoconcentration effect.** So far, we neglected a possible field dependence of the chemical potential  $\mu_v$  of oxygen vacancies. However, in high enough applied magnetic fields  $B$ , the field-induced change of the chemical potential  $\Delta\mu_v(B) \equiv \mu_v(B) - \mu_v(0)$  becomes tangible and should be taken into account. As is well-known [19, 20], in a superconducting state  $\Delta\mu_v(B) = -M(B)B/n$ , where  $M(B)$  is the corresponding magnetization, and  $n$  is the relevant carriers number density. At the same time, within our scenario, the chemical potential of a single oxygen vacancy  $\mu_v$  depends on the concentration of oxygen vacancies (through deficiency parameter  $\delta$ ). As a result, two different effects are possible related respectively to magnetic field dependence of  $\mu_v(B)$  and to its dependence on magnetization  $\mu_v(M)$ . The former is nothing else but a superconducting analog of the so-called *magnetoconcentration* effect (which was predicted and observed in inhomogeneously doped semiconductors [21]) with field-induced creation of oxygen vacancies  $c_v(B) = c_v(0) \exp(-\Delta\mu_v(B)/k_B T)$ , while the latter (as we shall see in the next Section) results in a “fishtail”-like behavior of the magnetization. Let us start with the magnetoconcentration effect. Fig.2 depicts the predicted field-induced creation of oxygen vacancies  $\delta(B) = 1 - c_v(B)$  using the above-obtained magnetization  $M(B, \delta)$  (see Fig.1 and Eq.(5)). We also assumed,

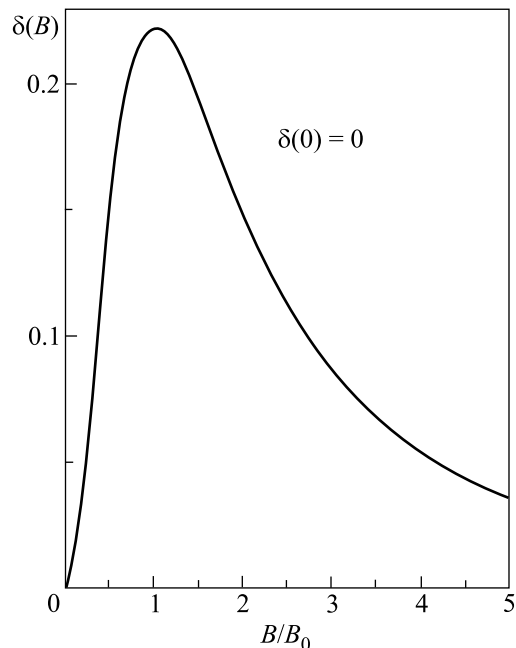


Fig.2. Magnetic field dependence of the oxygen deficiency parameter  $\delta(B)$  (magnetoconcentration effect)

for simplicity, a complete stoichiometry of the system in a zero magnetic field (with  $\delta(0) = 1 - c_v(0) = 0$ ). Notice that  $\delta(B)$  exhibits a maximum at  $\delta_c \approx 0.23$  for applied fields  $B = B_0$  (in agreement with the classical percolative behavior observed in non-stoichiometric  $YBa_2Cu_3O_{7-\delta}$  samples [3, 4, 15]). Finally, let us show that in underdoped crystals the above-discussed osmotic mechanism of oxygen transport is indeed much more effective than a traditional diffusion. Using typical YBCO parameters [14],  $\epsilon = 0.01$ ,  $\Omega_0 = a_0^3$  with  $a_0 = 0.2$  nm, and  $K = 115$  GPa, we have  $\mu_v(0) = \epsilon K \Omega_0 \approx 1$  meV for a zero-field value of the chemical potential in HTS crystals, which leads to creation of excess vacancies with concentration  $c_v(0) = e^{-\mu_v(0)/k_B T} \approx 0.7$  (equivalent to a deficiency value of  $\delta(0) \approx 0.3$ ) at  $T = T_c$ , while the probability of oxygen diffusion in these materials (governed by a rather high activation energy  $U_d \approx 1$  eV) is extremely slow under the same conditions because  $D \propto e^{-U_d/k_B T_c} \ll 1$ . On the other hand, the change of the chemical potential in applied magnetic field can reach as much as [20]  $\Delta\mu_v(B) \approx 0.5$  meV for  $B = 0.5$  T, which is quite comparable with the above-mentioned zero-field value of  $\mu_v(0)$ .

**6. Analog of “fishtail” anomaly.** Let us turn now to the second effect related to the magnetization dependence of the chemical potential  $\mu_v(M(B))$ . In this case, in view of Eq.(2), the phase difference will acquire an extra  $M(B)$  dependent contribution and as a result the r.h.s. of Eq.(5) will become a nonlin-

ear functional of  $M(B)$ . The numerical solution of this implicit equation for the resulting magnetization  $m_f = M(B, \delta(B))/M_0(0)$  is shown in Fig.3 for the two values of zero-field deficiency parameter  $\delta(0)$ . As is

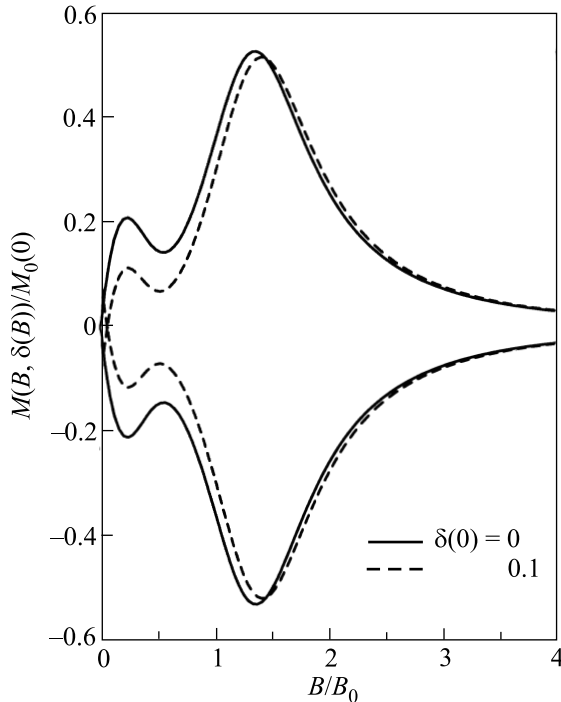


Fig.3. A “fishtail”-like behavior of magnetization  $m_f = M(B, \delta(B))/M_0(0)$  in applied magnetic field  $B/B_0$  in the presence of magnetoconcentration effect (with field-induced oxygen vacancies  $\delta(B)$ , see Fig.2) for two values of field-free deficiency parameter:  $\delta(0) = 0$  (solid line), and  $\delta(0) = 0.1$  (dashed line)

clearly seen,  $m_f$  exhibits a field-induced “fishtail”-like behavior typical for underdoped crystals with intragrain granularity (for symmetry and better visual effect we also plotted  $-m_f$  in the same figure). The extra extremum of the magnetization appears when the applied magnetic field  $B$  matches an intrinsic chemomagnetic field  $B_\mu(\delta(B))$  (which now also depends on  $B$  via the above-discussed magnetoconcentration effect). Notice that a “fishtail” structure of  $m_f$  manifests itself even at zero values of field-free deficiency parameter  $\delta(0)$  (solid line in Fig.3) thus confirming a field-induced nature of intrinsic granularity [1, 3, 13–15]. At the same time, even a rather small deviation from the zero-field stoichiometry (with  $\delta(0) = 0.1$ ) immediately brings about a paramagnetic Meissner effect at low magnetic fields. Thus, the present model predicts appearance of two in-

terrelated phenomena, Meissner paramagnetism at low fields and “fishtail” anomaly at high fields. It would be very interesting to verify these predictions experimentally in non-stoichiometric superconductors with pronounced networks of planar defects.

This work was done during my stay in L’Aquila and was funded by the Italian Institute for the Physics of Matter (INFM). I thank Giacomo Rotoli and Giovanni Filatrella for hospitality and interesting discussions on the subject.

1. K. M. Lang, V. Madhavan, J. E. Hoffman et al., *Nature* **415**, 412 (2002).
2. V. F. Gantmakher, *Usp. Fiz. Nauk* **172**, 1283 (2002).
3. M. Daeumling, J. M. Seuntjens, D. C. Larbalestier et al., *Nature* **346**, 332 (1990); I. M. Babich and G. P. Mikitik, *JETP Lett.* **64**, 586 (1996).
4. V. F. Gantmakher, A. M. Neminskii, and D. V. Shovkun, *JETP Lett.* **52**, 630 (1990).
5. See, e.g., *Mesoscopic and Strongly Correlated Electron Systems-II*, Ed. M. V. Feigel’man, V. V. Ryazanov, and V. B. Timofeev, *Phys. Usp. (Suppl.)* **44** (10) (2001).
6. L. B. Ioffe, M. V. Feigel’man, A. Ioselevich et al., *Nature* **415**, 503 (2002).
7. V. Kataev, N. Knauf, W. Braunisch et al., *JETP Lett.* **58**, 636 (1993); A. K. Geim, S. V. Dubonos, J. G. S. Lok et al., *Nature* **396**, 144 (1998).
8. C. De Leo and G. Rotoli, *Phys. Rev. Lett.* **89**, 167001 (2002).
9. V. V. Ryazanov, V. A. Oboznov, A. Yu. Rusanov et al., *Phys. Rev. Lett.* **86**, 2427 (2001).
10. A. A. Golubov, M. Yu. Kupriyanov, and Ya. V. Fominov, *JETP Lett.* **75**, 588 (2002).
11. E. Z. Meilikhov, *JETP* **83**, 803 (1996).
12. S. Sergeenkov, *JETP Lett.* **70**, 36 (1999).
13. G. Yang, P. Shang, S. D. Sutton et al., *Phys. Rev.* **B48**, 4054 (1993).
14. A. Gurevich and E. A. Pashitskii, *Phys. Rev.* **B56**, 6213 (1997).
15. B. H. Moeckley, D. K. Lathrop, and R. A. Buhrman, *Phys. Rev.* **B47**, 400 (1993).
16. L. A. Girifalco, *Statistical Physics of Materials*, A Wiley-Interscience Publication, New York, 1973.
17. S. Sergeenkov, *J. Appl. Phys.* **78**, 1114 (1995).
18. S. Sergeenkov, *JETP Lett.* **76**, 170 (2002).
19. A. A. Abrikosov, *Fundamentals of the Theory of Metals*, Elsevier, Amsterdam, 1988.
20. S. Sergeenkov and M. Ausloos, *JETP* **89**, 140 (1999).
21. A. A. Akopyan, S. S. Bolgov, A. P. Savchenko et al., *Sov. Phys. Semicond.* **24**, 1167 (1990).